

## **INFLUENCE OF THE PRE-STRESSED AREAS ON CIRCULAR DISC VIBRATIONS**

**M. Nad'**

**Summary:** *One of the techniques to achieve of required dynamical properties of the circular disc is presented in this paper. This technique is based on initiation of pre-stressed areas in the disc plane. In-plane residual stresses are created by appropriate technological treatments – roll-tension of annulus or volume transformation of disc part. The effects of in-plane residual stresses on dynamical properties of circular disc are analysed. The natural frequency characteristics for various rolling position and various rolling depth of the annulus are obtained by modal analysis using Finite Element Method (FEM). The role of residual stresses is assessed from the change in natural frequencies and modal shapes.*

### **1. Introduction**

The circular discs are structural elements widely used in the structural and processing applications. One of the most used geometric shape for processing and cutting operation material is thin circular disc - circular saw blade. Circular saw blades are widely used tools for cutting and forming metal and non-metal materials.

The quality of the cutting is mostly influenced by dynamical behaviour of circular saw blade in cutting process. The large transversal displacements of circular saw blade, induced by rotation of circular saw blade and external effects, occur during cutting process. The loss of dynamical stability and arising of resonance state are caused by the reduction of natural frequencies of the disc due to the thermal compressive stress induced by cutting heat in the peripheral region. In dependence on cutting conditions, the temperature of cutting in the peripheral region increases up 500° C. It is necessary to eliminate these inconvenient effects by some design or technological treatments.

One of the techniques of the disc modifications to achieve the required dynamic properties is to initiate pre-stress in disc plane. This is concerned primarily with “tuning” of dynamical properties of vibrating circular discs by technological treatments inducing the residual in-plane stresses. It is possible to obtain the disc in-plane stress either roll-tension of disc surface or volume transformation of disc part. In the roll-tensioning process, a disc is compressed within a certain annular contact zone between two opposing rollers. The contact zone of circular saw blade is plastically deformed and the residual stresses occur in whole disc plane. The effects of residual stresses induced by roll-tension on dynamical properties (natural frequencies, mode shapes) are analysed.

The natural frequency characteristics for various rolling position and various rolling depth of the annulus are obtained by modal analysis using Finite Element Method (FEM). The role of residual stresses obtained by rolling is assessed from the change in natural frequencies and modal shapes.

## 2. Formulation of the problem

We consider an isotropic homogeneous circular disc of outer radius  $R_0$ , inner radius  $r_0$  and thickness  $h$  (Fig.1). The radius  $r_0$  specifies a circle where is the disc clamped by flanges. The plastically deformed annulus is determined by inner radius  $r_1$  and outer radius  $r_2$ .

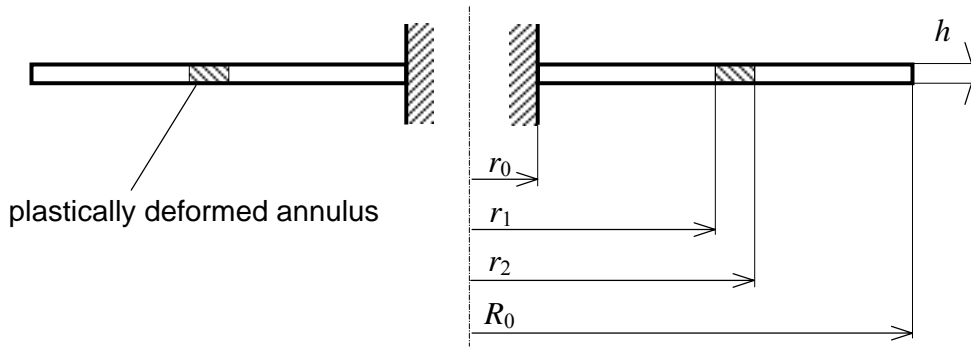


Fig.1 The circular disc with plastically deformed annulus.

The fundamental considerations and derivation of equations of motion are based on Kirchhoff's assumptions. The field of displacements in the cylindrical coordinates  $r$ ,  $\varphi$ ,  $z$ , using Kirchhoff plate theory can be written as

$$\begin{aligned} u_r(r, \varphi, z, t) &= u(r, \varphi) - z \frac{\partial w(r, \varphi, t)}{\partial r}, \\ v_\varphi(r, \varphi, z, t) &= v(r, \varphi) - \frac{z}{r} \frac{\partial w(r, \varphi, t)}{\partial \varphi}, \\ w_z(r, \varphi, z, t) &\cong w(r, \varphi), \end{aligned} \quad (1)$$

where  $u(r, \varphi)$ ,  $v(r, \varphi)$  and  $w(r, \varphi)$  are displacement of point laying on neutral plane of the circular disc in coordinate directions.

The stress-strain relations in the cylindrical coordinates can be written

$$\boldsymbol{\sigma} = \mathbf{D}\boldsymbol{\varepsilon}, \quad (2)$$

where  $\boldsymbol{\sigma}$  is stress vector,  $\boldsymbol{\varepsilon}$  is strain vector,  $\mathbf{D}$  is elasticity matrix.

Using the finite element formulation, the equation of motion for a free vibration of circular disc modelled by FEM is described by expression

$$\mathbf{M}\ddot{\mathbf{q}} + \mathbf{K}\mathbf{q} = \mathbf{0}, \quad (3)$$

where  $\mathbf{M}$  is mass matrix,  $\mathbf{K}$  is stiffness matrix,  $\ddot{\mathbf{q}}$  and  $\mathbf{q}$  are vectors nodal accelerations and nodal displacements, respectively.

Generally, after initiation of in-plane stress fields, the stress-strain relations with initial stress and initial strain are given by

$$\boldsymbol{\sigma} = \mathbf{D}(\boldsymbol{\varepsilon} - \boldsymbol{\varepsilon}_0) + \boldsymbol{\sigma}_0, \quad (4)$$

where  $\boldsymbol{\sigma}_0$  - initial stress vector,  
 $\boldsymbol{\varepsilon}_0$  - initial strain vector.

The equation of motion for a free vibration of in-plane stressed disc modelled by FEM is described by expression

$$\mathbf{M}\ddot{\mathbf{q}} + (\mathbf{K} + \mathbf{K}_\sigma)\mathbf{q} = \mathbf{0}, \quad (5)$$

where  $\mathbf{K}_\sigma$  - stiffness matrix following from stress distribution induced by rolling.

The mass distribution of pre-stressed circular disc after rolling is not changed, but the residual stress distribution is developed in disc plane in consequence of the bending stiffness of disc varies greatly. Using equation (5), the natural frequencies and modal shapes of a circular disc with roll induced residual stress distribution can be obtain from the following eigen-value problem

$$(\mathbf{K} + \mathbf{K}_\sigma - \omega_i^2 \mathbf{M})\boldsymbol{\psi}_i = \mathbf{0}, \quad (6)$$

where  $\omega_i$  - natural frequency of the circular disc,  
 $\boldsymbol{\psi}_i$  - eigen-vector describing modal shape of the circular disc.

In order to calculate the variation of disc stiffness  $\mathbf{K}_\sigma$  after rolling, we must know the residual stress distribution in a disc plane. To the determination of residual stress distribution, the method of thermal stress loading is used. The thermal expansion embedded to annular fields induces the stress distribution in circular disc, which is analogous to the stress distribution initiated by roll-tension.

The natural frequencies and modal shapes of circular disc with residual stress distribution for different rolling position, depth and width of rolled annulus can be determined from calculation model which is described by equation (6). To obtain optimal rolling radius, it is necessary to determine the natural frequency curves for the various position of center radius of the rolled annulus  $r_c = (r_2 + r_1)/2$  ( $r_1$  - inner radius,  $r_2$  - outer radius of rolled annulus, see Fig.1).

### 3. Numerical example and simulations

We consider a circular disc of the outer diameter 240 mm, thickness 1.8 mm and flange diameter is 50 mm. The disc for analysis is assumed to be perfectly fixed in region  $r \leq r_0$  (see Fig.1). The outer edge of disc is free. The depth of the rolling is varied and for simulation are used values 1  $\mu\text{m}$ , 2  $\mu\text{m}$ , 3  $\mu\text{m}$  and 4  $\mu\text{m}$ . The effect of the position and depth of roll-tensioning annular field and number of annular fields on natural frequencies is investigated. The dynamical properties of the disc were determined using FEM by software program ANSYS.

The distribution of radial and tangential in-plane residual stresses of circular discs with one roll-tension annular part (for example  $r_c = 0.05$  m) is shown on figure 2. The width of plastically deformed annular field is  $r_2 - r_1 = 10$  mm and depth is  $\Delta z = 1$   $\mu\text{m}$

The distribution of radial and tangential in-plane residual stresses of circular discs with two roll-tensioning annular fields (for example  $r_{c1} = (r_{12} + r_{11})/2 = 0.03$  m,  $r_{c2} = (r_{22} + r_{21})/2 = 0.07$  m;

$r_{ci}$  is center radius of the  $i$ -th annulus,  $r_{i1}$ , resp.  $r_{i2}$  are inner, resp. outer radius of the  $i$ -th annulus) is shown on figure 3. The width of both plastically deformed annular fields is 10 mm and depth is  $\Delta z = 1 \mu\text{m}$ .

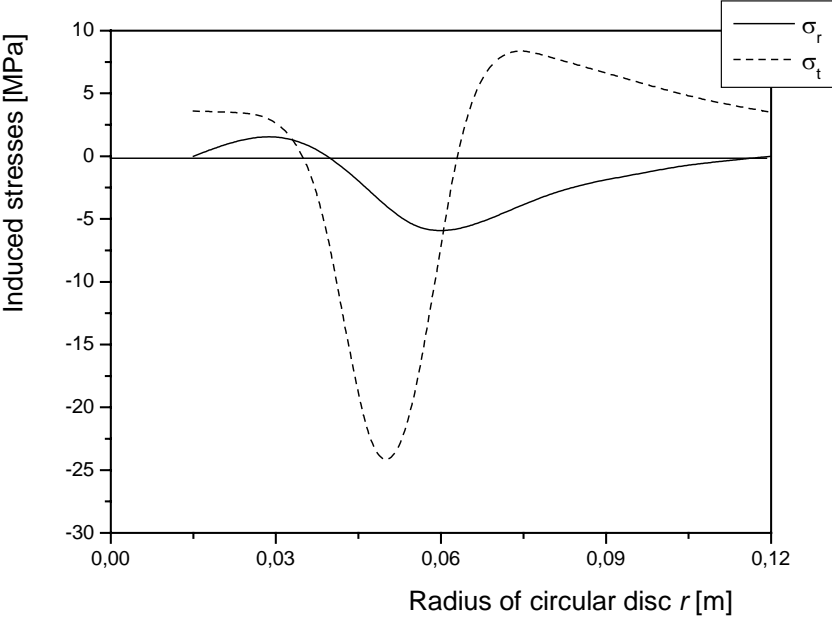


Fig. 2 Distribution of radial and tangential stresses of circular disc with one pre-stressed annular part ( $r_c = 0.05$  m,  $\Delta z = 1 \mu\text{m}$ ).

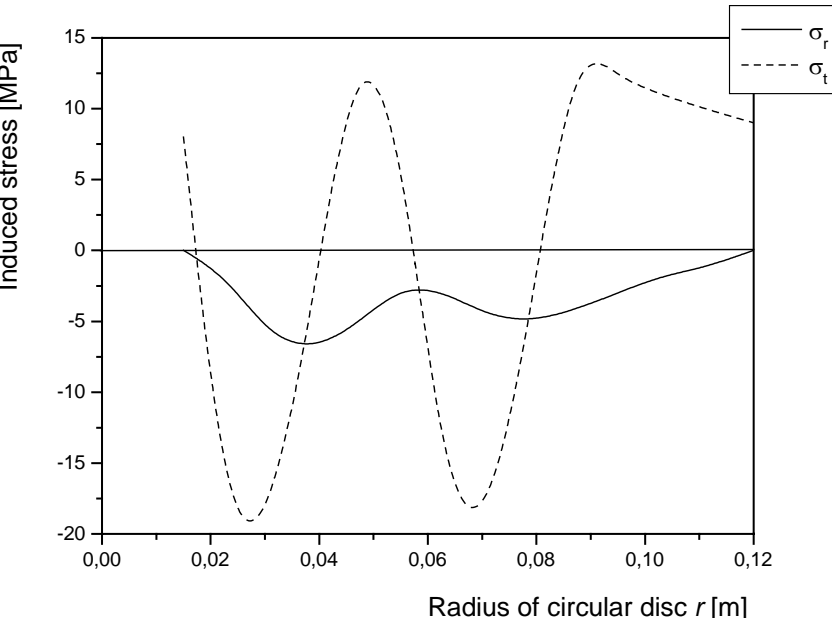


Fig. 3 Distribution of radial and tangential stresses of circular disc with two pre-stressed annular fields ( $r_{c1} = 0.03$  m,  $\Delta z_1 = 1 \mu\text{m}$ ;  $r_{c2} = 0.07$  m,  $\Delta z_2 = 1 \mu\text{m}$ ).

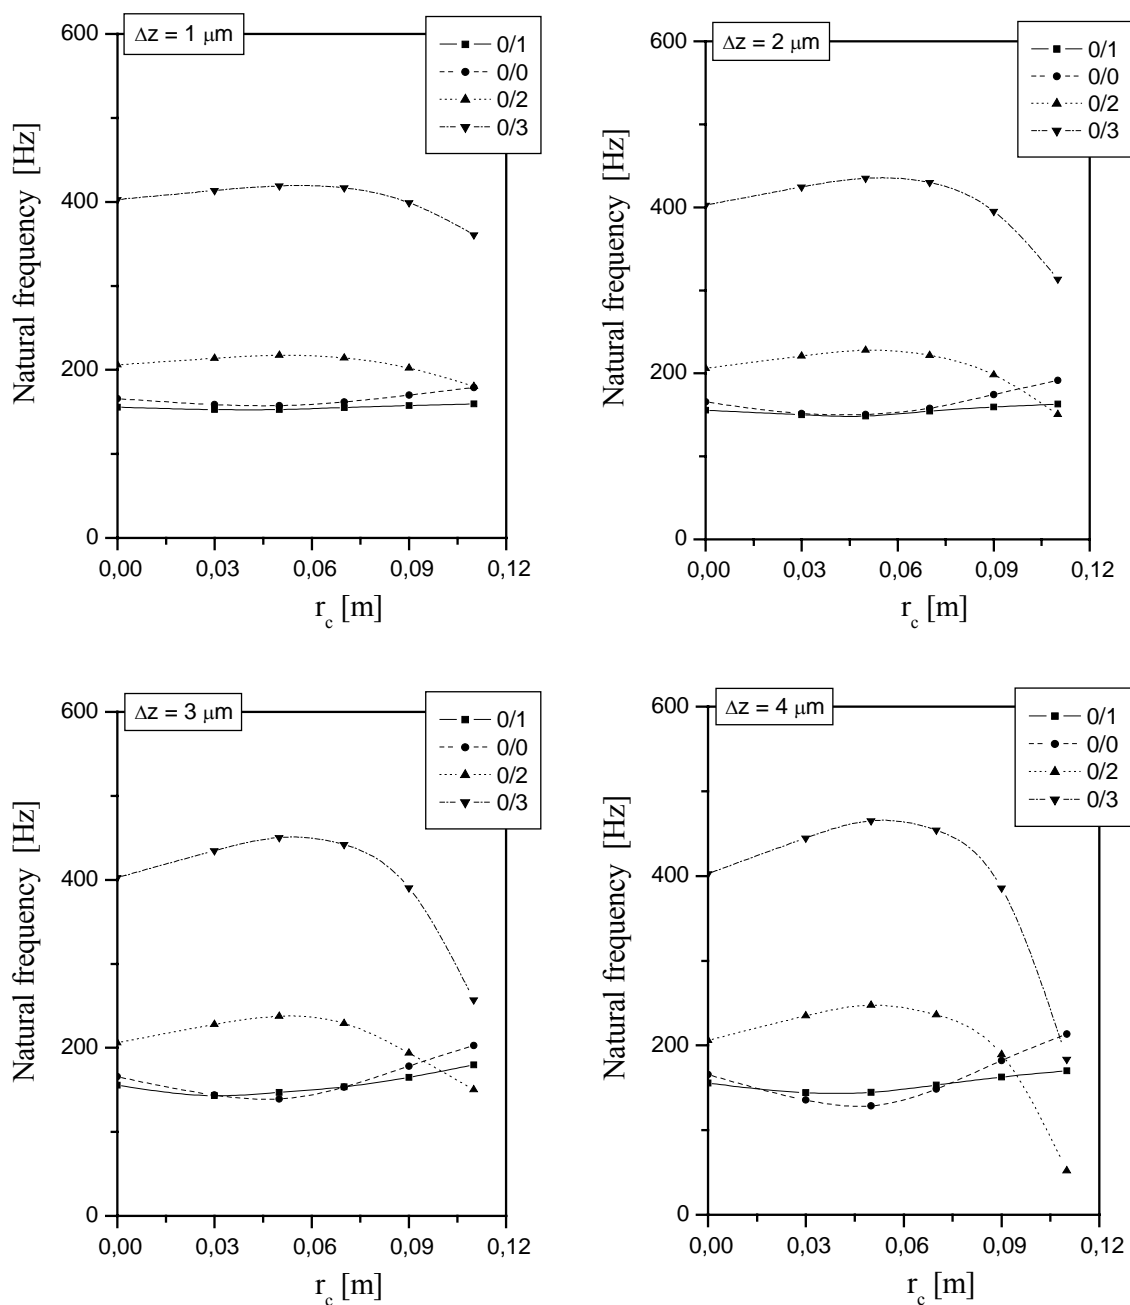


Fig. 4 Natural frequency vs. center of rolling  $r_c$  for different depth of rolling  $\Delta z$  (circular disc with one pre-stressed annular field).

Figure 4 shows the natural frequency curves of the modal shapes 0/1, 0/0, 0/2, 0/3 (nodal circles/nodal lines) for different depth of rolling ( $\Delta z = 1,0 \div 4,0 \mu\text{m}$ ) calculated by FEM when  $r_c$  varies from 0,03 m to 0,11 m. The natural frequencies of circular disc before rolling are marked by  $r_c = 0.0$  m. The tendency of curves for modal shapes 0/1 and 0/0 differs from curves for modal shapes 0/2 and 0/3. The natural frequencies of the modal shapes 0/2 and 0/3 increase with  $r_c$  until the maximum values near  $r_c \approx 0.055$  m are reached; then they decrease. Contrary to this, the natural frequencies of the modal shapes 0/1 and 0/0 decrease with  $r_c$  and for  $r_c \approx 0.046$  m reach the minimum; then they increase.

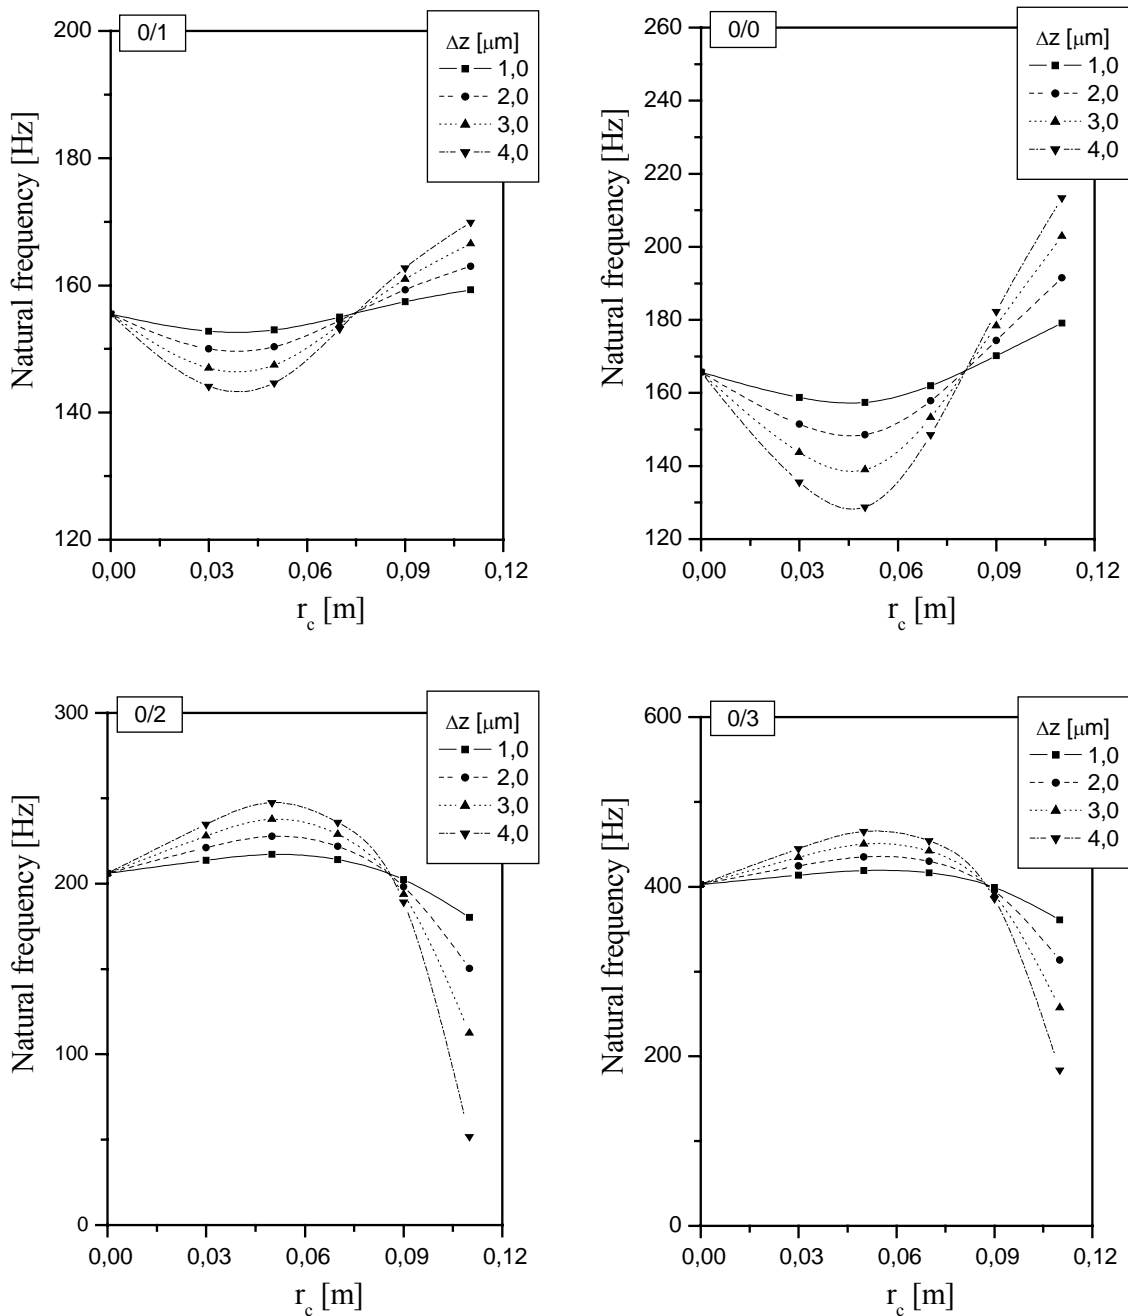


Fig.5 Natural frequency vs. center of rolling for different modal shapes (circular disc with one pre-stressed annular field).

On figure 5, the natural frequency curves of the individual modal shapes 0/1, 0/0, 0/2, 0/3 in dependency of depth of rolling are shown. The natural frequencies of the modal shapes 0/1 and 0/0 decrease with  $r_c$  until the minimum values near  $r_c \cong 0.046$  m are reached; then they increase. Contrary to this, the natural frequencies of the modal shapes 0/2 and 0/3 increase with  $r_c$  and for  $r_c \cong 0.055$  m reach the minimum; then they increase. The effect of depth of rolling on natural frequency is evident from these graphs.

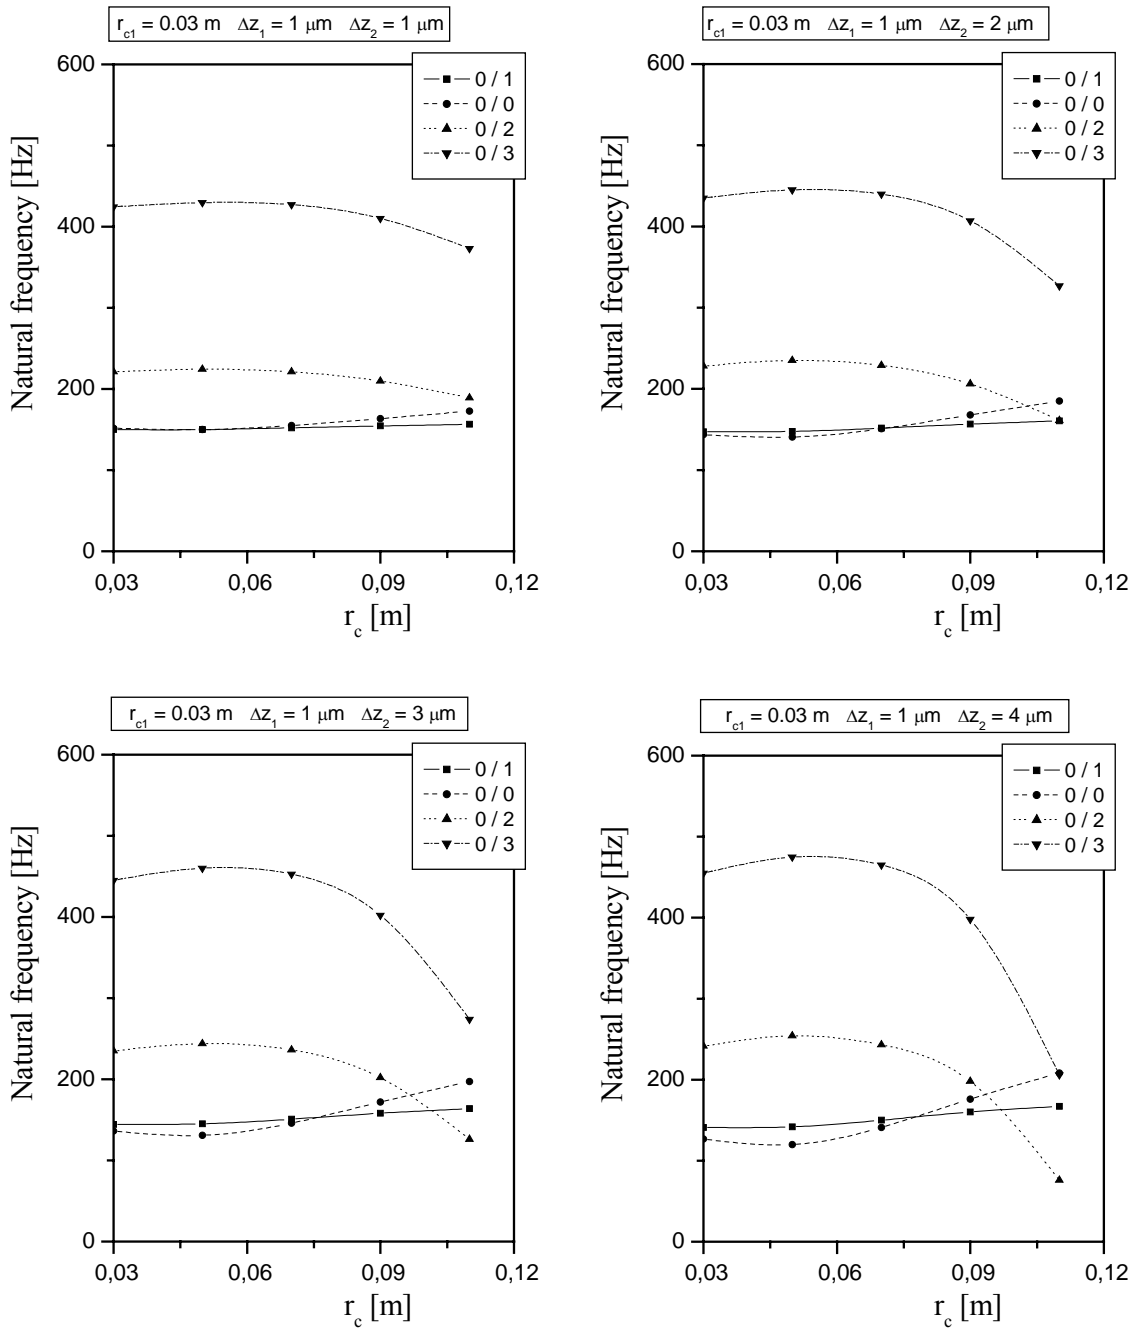


Fig.6 Natural frequency vs. center of rolling for different modal shapes (circular disc with two pre-stressed annular fields  $r_{c1} = 0,03$  m,  $r_{c2} = 0,03 \div 0,12$  m).

The natural frequency curves of circular disc with two pre-stressed annular fields ( $r_{c1}$  is constant value 0,03 m and  $r_{c2}$  varies from 0,03 m to 0,12 m) are shown on figure 6. The effect of two pre-stressed annular fields on dynamical properties of disc is similar as for disc with one pre-stressed field.

The effect of thermal compressive stress induced by cutting heat in the peripheral region we can see for  $r_c = 0.11$  m, where natural frequencies of the modal shapes 0/2 and 0/3 for different depth of rolling are lower then natural frequencies of the modal shapes 0/1 and 0/0. For this case, the

resonance of circular disc arises for lower frequencies. The reason why natural frequencies are varied due to rolling is that stiffness characteristics within the disc are locally changed by stress distribution.

#### **4. Conclusions**

The theoretical formulation and calculation model for analysis of dynamical properties of circular disc with residual stress distribution are presented. Finite element analysis for estimating of natural frequencies was used. The appropriate rolling position is necessary to determine from natural frequency characteristics calculated for various center of rolling.

#### **5. Acknowledgement.**

The author wish to thank the financial support of VEGA MS SR and SAV project 1/9102/2 and project MVTS-RF/CR/SR/2.

#### **6. References**

- Kuratani, F. & Yano, S. (2000) Vibration analysis of a circular disk tensioned by rolling using finite element method. *Archive of Applied Mechanics*, 70, pp. 279-288.
- Markuš, Š. & Nánási T. (1981) Significance of in-plane inertia forces in the vibration analysis of three-layered circular plates. *Journal of Sound and Vibration*, 76, 3, pp. 421-441.
- Nad, M. (2002) The effect of the pre-stressed areas on circular plate vibrations, in: *Proc. of the International Acoustic Conference - Noise and Vibration in Practice*, Kočovce, pp.115-120.